



BSI Standards Publication

Wood-based panels — Determination of formaldehyde release

Part 3: Gas analysis method

National foreword

This British Standard is the UK implementation of EN ISO 12460-3:2020. It is identical to ISO 12460-3:2020. It supersedes BS EN ISO 12460-3:2015, which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee B/541, Wood based panels.

A list of organizations represented on this committee can be obtained on request to its committee manager.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2020
Published by BSI Standards Limited 2020

ISBN 978 0 539 02250 6

ICS 79.060.01

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 October 2020.

Amendments/corrigenda issued since publication

Date	Text affected
------	---------------

EUROPEAN STANDARD

EN ISO 12460-3

NORME EUROPÉENNE

EUROPÄISCHE NORM

October 2020

ICS 79.060.01

Supersedes EN ISO 12460-3:2015

English Version

Wood-based panels - Determination of formaldehyde release - Part 3: Gas analysis method (ISO 12460-3:2020)

Panneaux à base de bois - Détermination du dégagement de formaldéhyde - Partie 3: Méthode d'analyse de gaz (ISO 12460-3:2020)

Holzwerkstoffe - Bestimmung der Formaldehydabgabe - Teil 3: Gasanalyse-Verfahren (ISO 12460-3:2020)

This European Standard was approved by CEN on 2 October 2020.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels

European foreword

This document (EN ISO 12460-3:2020) has been prepared by Technical Committee ISO/TC 89 "Wood-based panels" in collaboration with Technical Committee CEN/TC 112 "Wood-based panels" the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by April 2021, and conflicting national standards shall be withdrawn at the latest by April 2021.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN ISO 12460-3:2015.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

Endorsement notice

The text of ISO 12460-3:2020 has been approved by CEN as EN ISO 12460-3:2020 without any modification.

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	1
5 Reagents	1
6 Apparatus	2
6.1 Main composites of test apparatus (see Figure 1).....	2
6.2 Laboratory equipment.....	3
7 Sampling and preparation of test pieces	4
7.1 Preparation of test pieces.....	4
7.2 Selection of test pieces for factory production control.....	5
7.3 Selection of test pieces for other purposes.....	5
7.4 Preparation of test pieces in case of dispute.....	5
8 Procedure	5
8.1 Number of determinations.....	5
8.2 Determination of moisture content.....	5
8.3 Determination of formaldehyde release.....	5
8.3.1 General.....	5
8.3.2 Determination of formaldehyde release — Option 1.....	7
8.3.3 Determination of formaldehyde release — Option 2.....	7
8.3.4 Determination of formaldehyde release — Option 3.....	7
8.3.5 Determination of formaldehyde release — Option 4.....	7
8.4 Determination of formaldehyde content of the absorber solutions.....	7
8.4.1 General.....	7
8.4.2 Principle.....	8
8.4.3 Analytical procedure.....	8
8.4.4 Calibration curve.....	8
9 Expression of results	10
9.1 Gas analysis value.....	10
9.2 Calculation of results.....	10
9.2.1 Calculation of results of test pieces.....	10
9.2.2 Calculation of emission report value.....	11
9.3 Moisture content.....	11
10 Test report	11
Bibliography	13

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 89, *Wood based panels*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 112, *Wood based panels*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This second edition cancels and replaces the first edition (ISO 12460-3:2015), which has been technically revised in order to improve the detection limit and the reproducibility of the method with regard to boards with low formaldehyde content.

The main changes compared to the previous edition are as follows:

- test period can be reduced from 4 h to 3 h;
- in [8.3](#) four different options to determine the formaldehyde release are introduced;
- conditioning procedure for decor finish foils specified in [7.1](#).

A list of all parts in the ISO 12460 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Wood-based panels — Determination of formaldehyde release —

Part 3: Gas analysis method

1 Scope

This document specifies a procedure for determination of accelerated formaldehyde release from uncoated and coated wood-based panels using the gas analysis method. The procedure is also suitable for the testing of other materials (e.g. edge bands, floor coverings, foams, foils, laminated wood products, veneered wood products, coated wood products).

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 16979, *Wood-based panels — Determination of moisture content*

ISO 16999, *Wood-based panels — Sampling and cutting of test pieces*

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

4 Principle

A test piece of known surface area is placed in a closed chamber in which the temperature, humidity, airflow, and pressure are controlled to defined values. Formaldehyde released from the test pieces mixes with the air in the chamber. This air is continually drawn from the chamber and passes through gas wash bottles, containing water, which absorbs the released formaldehyde. At the end of the test, the formaldehyde concentration is determined photometrically or fluorimetrically. The formaldehyde release is calculated from this concentration, the sampling time, and the exposed area of the test pieces and is expressed in milligrams per square meter and hour (mg/m²h).

5 Reagents

Reagents of recognized analytical purity and distilled or demineralised water (referred throughout the following text as distilled water) shall be used for the analysis.

5.1 4 ml acetylacetone solution are added to a 1 000 ml volumetric flask and made up to the mark with distilled water.

5.2 200 g ammonium acetate solution are dissolved with distilled water in a 1 000 ml volumetric flask and made up to the mark.

Optionally, a premixed reagent of acetylacetone and ammonium acetate as described in ISO 12460-4 can be used.

5.3 Formaldehyde solution, commercially available (concentration typically between 35 % mass fraction to 40 % mass fraction).

5.4 Standard iodine solution, $c(I_2) = 0,05 \text{ mol/l}$.

5.5 Standard sodium thiosulphate solution, $c(Na_2S_2O_3) = 0,1 \text{ mol/l}$.

5.6 Standard sodium hydroxide solution, $c(NaOH) = 1 \text{ mol/l}$.

5.7 Standard sulphuric acid solution, $c(H_2SO_4) = 1 \text{ mol/l}$.

5.8 Starch solution, 1 % mass fraction.

6 Apparatus

6.1 Main composites of test apparatus (see [Figure 1](#))

6.1.1 Dust or particle filter.

6.1.2 Formaldehyde filter (bottle filled with water, silicagel or other formaldehyde absorber).

6.1.3 Desiccator, 500 ml, containing silica gel.

6.1.4 Air pump.

6.1.5 Needle valve.

6.1.6 Equipment for measuring rate of air flow through apparatus.

NOTE Needle valve and equipment for measuring rate of air flow can be replaced by a mass flow controller.

6.1.7 Test chamber (diameter: 90 mm to 100 mm with a length which gives an internal volume of $4\,000 \pm 200$ ml with double casing of stainless steel or glass).

6.1.8 Heating equipment for air (e.g. copper coil inside the double casing).

6.1.9 Thermostat.

6.1.10 Magnetic valves.


6.1.11 Pairs of gas wash bottles, 100 ml or optionally, pairs of gas wash bottles, 30 ml.

6.1.12 Pressure monitor.

6.1.13 Temperature monitor.

6.1.14 Test piece holder, constructed as a shelf with three rods made from stainless steel or another inert material.

NOTE The test apparatus described in [Figure 1](#) is based on a waterborne heating system. A test apparatus with an electrical heating system can be used optionally.

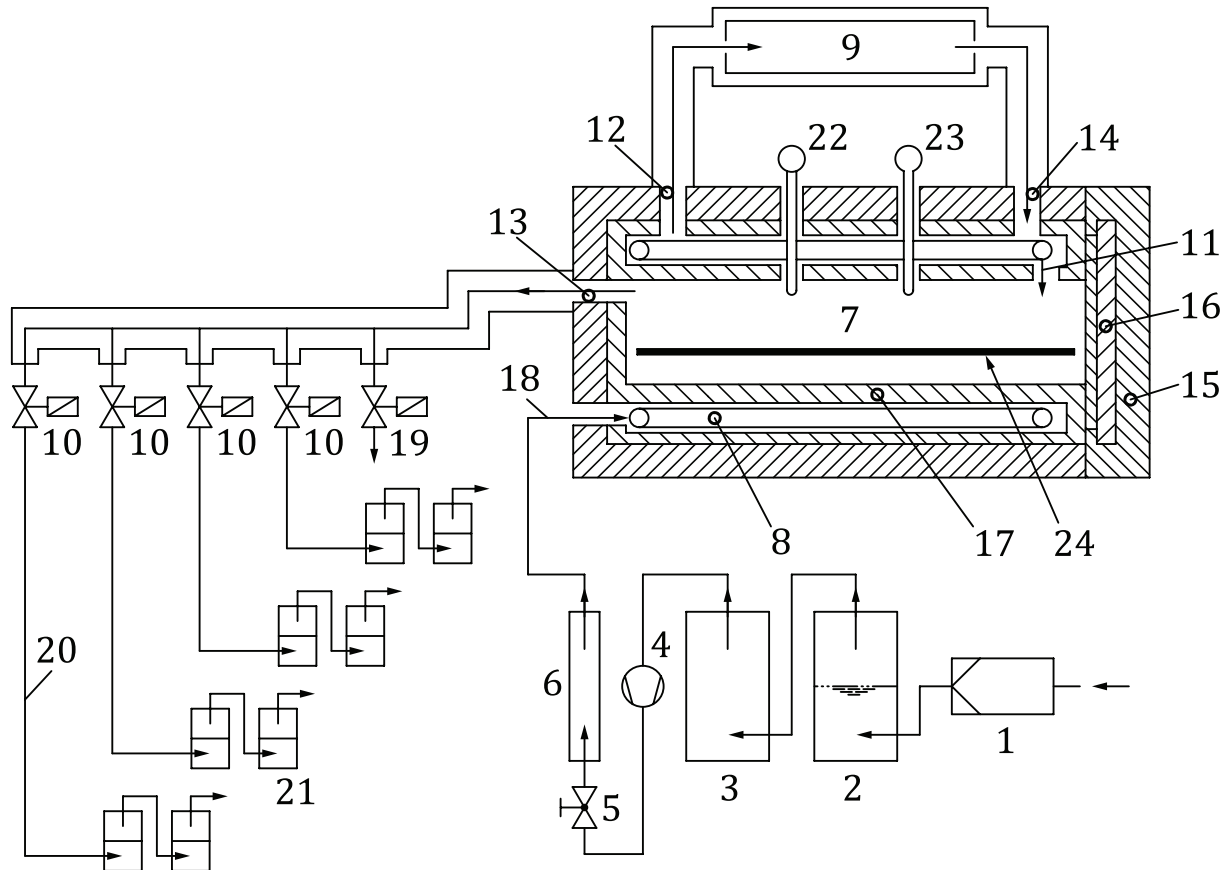

Key

- | | | | |
|----|---------------------------------------|----|------------------------------|
| 1 | dust or particle filter | 13 | outlet of test air |
| 2 | formaldehyde filter | 14 | heating medium (inlet) |
| 3 | desiccator | 15 | insulation |
| 4 | air pump | 16 | test chamber door |
| 5 | needle valve | 17 | double casing |
| 6 | equipment for measurement of air flow | 18 | inlet for air (heating coil) |
| 7 | test chamber | 19 | magnetic valve for purging |
| 8 | heating coil | 20 | connection tube |
| 9 | thermostat | 21 | pairs of wash bottles |
| 10 | magnetic valves | 22 | pressure monitor |
| 11 | inlet of air (test chamber) | 23 | temperature monitor |
| 12 | heating medium (outlet) | 24 | test piece holder |

Figure 1 — Gas analysis test apparatus

6.2 Laboratory equipment

6.2.1 Ventilated oven, as described in ISO 16979 for determination of moisture content (if requested).

6.2.2 Spectrophotometer, with cells of 50 mm optical path length and capable of measuring absorbance at 412 nm.

6.2.3 Water bath, capable of maintaining a temperature of $(60 \pm 1) ^\circ\text{C}$.

6.2.4 Water bath, capable of maintaining a temperature in the range of $20 ^\circ\text{C}$ to $25 ^\circ\text{C}$.

6.2.5 Six volumetric flasks, 100 ml (calibrated at $20 ^\circ\text{C}$).

6.2.6 Four volumetric flasks, 250 ml or optionally, four volumetric flasks, 100 ml (calibrated at $20 ^\circ\text{C}$).

6.2.7 Two volumetric flasks, 1 000 ml (calibrated at $20 ^\circ\text{C}$).

6.2.8 Volumetric pipettes (calibrated at $20 ^\circ\text{C}$), 1 ml, 2 ml, 5 ml, 10 ml, 15 ml, 20 ml, 25 ml, 30 ml, 50 ml, 100 ml.

6.2.9 Six flasks, 50 ml (with stoppers).

6.2.10 Microburette.

6.2.11 Burette, 50 ml, graduated (calibrated at $20 ^\circ\text{C}$).

6.2.12 Balance, capable of measuring to 0,00 1 g.

7 Sampling and preparation of test pieces

7.1 Preparation of test pieces

Three test pieces, each with the dimensions of $(400 \pm 1) \text{ mm} \times (50 \pm 1) \text{ mm} \times$ board thickness, shall be prepared for the determination of formaldehyde release giving a total emitting surface area of $0,04 \text{ m}^2$.

If the sample available does not allow the preparation of test pieces of the specified dimension, then the combined emitting surface area of the test pieces(s) should be as close as possible to $0,04 \text{ m}^2$.

For testing layer glued materials (e.g. plywood, veneered particleboard), specimens shall be cut from the respective panel with the fibre direction of the faces perpendicular to the longitudinal axis of the specimen.

Each test piece has to be hermetically wrapped immediately after cutting and stored at ambient temperature.

Before testing, each test piece shall be stored hermetically wrapped at least one day at ambient temperature in order to improve the repeatability. For factory production control with hot test pieces, a valid correlation has to be established.

Test pieces shall be representative for the tested boards.

For testing, the test pieces shall be edge sealed with temperature resistant (i.e. $\geq 60 ^\circ\text{C}$) self-adhesive aluminium tape or an alternative sealing method if equivalence has been demonstrated. The emitting (unsealed) surface area of the sealed test piece has to be measured and calculated in square metres (m^2).

For decor finish foils it is recommended to pre-condition the material as follows in order to take into account inhomogeneity as to improve precision: 7 days at $(20 \pm 2) ^\circ\text{C}$ and $(65 \pm 5) \%$ relative humidity.

7.2 Selection of test pieces for factory production control

Sampling and cutting of the test pieces shall be performed in accordance with the principles of ISO 16999.

Test pieces are taken, uniformly distributed over the width of the (cooled) board, but excluding a 250 mm wide strip from the end of each board.

The formaldehyde determination should be carried out not more than 72 h after sampling.

7.3 Selection of test pieces for other purposes

The procedure of sampling, preparation of the test pieces, and conditioning (e.g. from boards already installed) shall be noted and described in the test report. The number and dimensions of the test pieces shall be as given in [7.1](#).

7.4 Preparation of test pieces in case of dispute

If this method is used in case of dispute, e.g. linked to disagreement about compliance and not otherwise agreed upon, the conditioning of the test pieces shall be carried out according to the following reference conditions.

The test pieces shall be conditioned to constant mass at a temperature of (20 ± 2) °C and a relative humidity of (65 ± 5) %.

Constant mass is considered to have been reached when the results of two successive weighings, carried out at intervals of not less than 24 h, do not differ by more than 0,1 % of the mass of the test pieces. Alternative two weeks of conditioning can be used.

Contamination of test pieces from other sources of formaldehyde during conditioning shall be avoided.

8 Procedure

8.1 Number of determinations

Determination shall always be made in duplicate using two different test pieces prepared according to [7.1](#). A third determination shall be carried out

- if the average emission value of the two determinations is $>1,0$ mg/m²h and the two replicates deviate more than 20 % of the average value, or
- if the average emission value of the determinations is $\leq 1,0$ mg/m²h and the two replicates deviate more than 0,2 mg/m²h from the average value.

For factory production control, a single determination can be sufficient.

8.2 Determination of moisture content

Moisture content shall be determined in accordance with ISO 16979 using a separate sample (see [7.1](#)).

8.3 Determination of formaldehyde release

8.3.1 General

The determination of formaldehyde release can be done by using different procedures, which are described as standard procedure (see [8.3.2](#)), to improve the sensitivity (see [8.3.3](#) and [8.3.4](#)) and to simplify the procedure (see [8.3.5](#)).

Seal the edges of the test pieces in accordance with [7.1](#).

Close chamber ([6.1.7](#)) and preheat it to $(60 \pm 0,5)$ °C.

For each test hour connect a pair of wash bottles (see [6.1.11](#)), each bottle containing between 8 ml to 40 ml absorber solution, in series to the outlet of each magnetic valve (see [6.1.10](#)) using flexible tubing by using four different options to improve the sensitivity of the analytical procedure and simplify the test method ([8.3.2](#) to [8.3.5](#)). The flexible tube shall be isolated in case of using the procedure of [8.3.3](#) or [8.3.5](#) in order to avoid condensation which requires the rinsing of the tube.

The absorber volume is chosen to maintain an overpressure of $(1\ 100 \pm 100)$ Pa in the test chamber. The pressure in the test chamber is monitored during the entire test period (see [6.1.12](#)).

Place a test piece in the preheated test chamber. After closing the test chamber and starting the test, the test piece is uniformly exposed to practically formaldehyde free, heated air $(60 \pm 0,5)$ °C with a relative humidity of ≤ 3 %. Immediately set the airflow into the chamber to (60 ± 3) l/h using the needle valve ([6.1.5](#)) and the air volume meter ([6.1.6](#)). This air is led into one of a series of pairs of gas wash bottles via a magnetic valve ([6.1.10](#)).

Instead of leading dry and clean air through gas wash bottles, dry and clean compressed air may be used optionally.

As the formaldehyde released from the test piece shall be determined at hourly intervals (up to 3 or 4 h from starting the test), a new series of gas wash bottles has to be connected and analysed every hour according to the analytical procedures given in [8.3.2](#) to [8.3.5](#). This exchange should be automatic.

For uncoated and coated particleboards and MDF with a thickness of at least 6 mm the test period may be reduced to 3 h. For all other material, a test period of 4 h is required. Tests can be carried out for 3 h provided that there is no significant difference with the results obtained after 4 h.

An overview of the 4 options for the determination of formaldehyde release is given in [Table 1](#).

Table 1 — Options for the analytical procedure

Option	Volume of wash bottle ml	Number of wash bottles connected to gas analysis apparatus	Number of wash bottles used for analysis	Type of absorber solution	Volume of absorber solution filled in wash bottles ml	Procedure for analysis	Volume of solution resp. volumetric flask after rinsing ml
1	100	2	2	distilled water	20 to 40	transfer and rinsing to defined volume of volumetric flask	250
2	30	2	2	distilled water	8 to 10	transfer and rinsing to defined volume of volumetric flask	100
3	100	2	2	distilled water	30 ^c	10 ml distilled water used for analysis (8.4.3)	not applicable
^a Mixed reagent: 10 ml distilled water/10 ml acetylacetone solution/10 ml ammonium acetate solution. ^b 2nd wash bottle can be filled with water for pressure adjustment only. ^c Other volumes may be used but the exact volume has to be determined and recorded for further calculation.							

Table 1 (continued)

Option	Volume of wash bottle ml	Number of wash bottles connected to gas analysis apparatus	Number of wash bottles used for analysis	Type of absorber solution	Volume of absorber solution filled in wash bottles ml	Procedure for analysis	Volume of solution resp. volumetric flask after rinsing ml
4	100	2	1 only 1st wash bottle ^b	mixed acetylacetone reagent ^a	30	to be analysed directly (8.4.3)	not applicable
^a Mixed reagent: 10 ml distilled water/10 ml acetylacetone solution/10 ml ammonium acetate solution. ^b 2nd wash bottle can be filled with water for pressure adjustment only. ^c Other volumes may be used but the exact volume has to be determined and recorded for further calculation.							

8.3.2 Determination of formaldehyde release — Option 1

Use two washing bottles with volume of 100 ml (see 6.1.11), each containing between 20 ml and 40 ml distilled water. Transfer the contents of each pair of gas wash bottles to a 250 ml volumetric flask (6.2.6). Rinse the bottles and their associated tubing thoroughly and transfer the rinsings to the flask.

8.3.3 Determination of formaldehyde release — Option 2

Use two gas wash bottles with volume of 30 ml (see 6.1.11), each containing between 8 ml and 10 ml distilled water. To improve the sensitivity of the analytical procedure, 100 ml volumetric flasks (6.2.5) may be used optionally, possibly in combination with 30 ml gas wash bottles. Fill to volume with distilled water and determine the formaldehyde content as specified in 8.4.

8.3.4 Determination of formaldehyde release — Option 3

Use two gas wash bottles with volume of 100 ml (see 6.1.11) and add 30 ml distilled water with a pipette (6.2.8) in each wash bottle as absorber solution. 10 ml are taken from the aqueous solution with a pipette (6.2.8) and added to 10 ml acetylacetone solution (5.1) and 10 ml ammonium acetate solution (5.2) in a stoppered flask (6.2.9).

8.3.5 Determination of formaldehyde release — Option 4

Using two gas wash bottles with volume of 100 ml (see 6.1.11), each containing 10 ml distilled water, 10 ml acetylacetone solution (5.1) and 10 ml ammonium acetate solution (5.2) as mixed reagent. Close the wash bottle, shake it, and heated for 10 min in a water bath (6.2.3) at 60 °C. The heated wash bottle is then cooled in a water bath (6.2.4) operated in a temperature range between 20 °C and 25 °C for at least 15 min protected from sunlight or is cooled to room temperature protected against the influence of light (for about 1 h).

Only the first wash bottle has to be analysed. The second wash bottle is only used to maintain the overpressure and can be rejected. To obtain the pressure of $(1\ 100 \pm 100)$ Pa for option 4 the volume of the second wash bottle can be 20 ml to 40 ml depending on the device used.

8.4 Determination of formaldehyde content of the absorber solutions

8.4.1 General

The formaldehyde content of the absorber solution from each 1 h sampling period shall be determined photometrically.

A fluorimetric determination may be used optionally. The description of a procedure is given, e.g. in EN 717-1. In case of using the analytical procedure described in [8.3.4](#) or [8.3.5](#) the photometric determination by using a cell with 10 mm path length can be used as described in ISO 12460-5.

8.4.2 Principle

The determination is based on the Hantzsch reaction in which aqueous formaldehyde reacts with ammonium ions and acetylacetone to yield diacetyldihydrolutidine (DDL). DDL has an absorption maximum at 412 nm. The reaction is highly specific to formaldehyde.

Other suitable photometric procedure can also be used.

8.4.3 Analytical procedure

10 ml are taken from the aqueous solution (see [8.3.2](#) to [8.3.4](#)) with a pipette ([6.2.8](#)) and added to 10 ml acetylacetone solution ([5.1](#)) and 10 ml ammonium acetate solution ([5.2](#)) in a stoppered flask ([6.2.9](#)).

To improve the sensitivity of the analytical procedure, equal amounts of aqueous solution (see [8.3.2](#) to [8.3.4](#)) and mixed reagent (see [5.2](#)) can be added optionally considering that the service life of such a mixture is shorter than the service life of the separate solutions.

The flask is stoppered or wash bottle closed (see [8.3.5](#)), shaken, and heated for 10 min in a water bath ([6.2.3](#)) at 60 °C. The heated flask is then cooled in a water bath ([6.2.4](#)) operated in a temperature range between 20 °C and 25 °C for at least 15 min protected from sunlight or is cooled to room temperature protected against the influence of light (for about 1 h).

The absorbance of this solution is determined at a wavelength of 412 nm against distilled water using a spectrophotometer ([6.2.2](#)). A blank value is determined in parallel with distilled water and taken into consideration in the determination of the gas analysis value.

8.4.4 Calibration curve

8.4.4.1 General

The calibration curve is produced from a standard formaldehyde solution, the concentration of which has been determined by iodometric titration. The calibration curve shall be checked at least once a week. It is possible to modify this frequency if it is proved that the slope of the standard curve does not deviate. In this case, the checking shall be made at least once a month and for each change of reagents.

8.4.4.2 Formaldehyde standard solution

Reagents:

— Standard iodine solution	$c(\text{I}_2)$	= 0,05 mol/l
— Standard sodium thiosulphate solution	$c(\text{Na}_2\text{S}_2\text{O}_3)$	= 0,1 mol/l
— Standard sodium hydroxide solution	$c(\text{NaOH})$	= 1 mol/l
— Standard sulphuric acid solution	$c(\text{H}_2\text{SO}_4)$	= 1 mol/l
— Starch solution		= 1 % mass fraction

The solutions shall be standardized before use.

About 1 ml formaldehyde solution (concentration 35 % to 40 %) is diluted in a 1 000 ml volumetric flask ([6.2.6](#)) with distilled water and made up to the mark. The exact formaldehyde concentration of this solution is determined as follows.

20 ml of the formaldehyde standard solution are mixed with 25 ml iodine solution and 10 ml sodium hydroxide solution. After 15 min standing protected from light, 15 ml of sulphuric acid solution is added. The surplus iodine is back-titrated with the thiosulphate solution. At the end of the titration, some drops of starch solution are added as an indicator. A blank test with 20 ml distilled water is carried out in parallel.

The formaldehyde content is calculated using [Formula \(1\)](#):

$$c(\text{HCHO}) = (V_0 - V) \times 15 \times c(\text{Na}_2\text{S}_2\text{O}_3) \times 1000/20 \quad (1)$$

where

$c(\text{HCHO})$ is the formaldehyde concentration, in milligrams per litre (mg/l);

$c(\text{Na}_2\text{S}_2\text{O}_3)$ is the thiosulfate concentration, in mols per litre (mol/l);

V_0 is the volume of thiosulphate titration solution for the blank test, in millilitres (ml);

V is the volume of thiosulphate titration solution for the test, in millilitres (ml).

NOTE 1 ml 0,1 mol/l thiosulphate solution corresponds to 1 ml 0,05 mol/l iodine solution and 1,5 mg formaldehyde.

Other titration procedures such as the method described by ISO 2227 or ISO 14184-1 can be used for the determination of the formaldehyde concentration.

8.4.4.3 Formaldehyde calibration solution

Using the concentration determined in [8.4.4.2](#), calculate the volume which will contain 3 mg formaldehyde. Transfer this volume using a microburette to a 1 000 ml volumetric flask and make up to the mark with distilled water. 1 ml of this calibration solution contains 3 µg formaldehyde.

8.4.4.4 Determination of the calibration curve

Pipette 0 ml, 1 ml, 2 ml, 5 ml, 10 ml, 20 ml, 50 ml, and 100 ml of formaldehyde calibration solution (see [8.4.4.3](#)) in 100 ml volumetric flasks and fill to volume with distilled water. 10 ml of each dilution are analysed photometrically by the same procedure as described above (see [8.4.3](#)). The absorbance values are plotted against the formaldehyde concentrations, c , (between 0 mg/ml and 0,003 mg/ml), and the slope, f , is calculated (see example in [Figure 2](#)).

9 Expression of results

9.1 Gas analysis value

For each 1 h sampling period, the gas analysis value, G_i , in milligrams per square metre and hour (mg/m²h) is determined and calculated using [Formula \(2\)](#):

$$G_i = \frac{(A_S - A_B) \times f \times V}{F} \quad (2)$$

where

- G_i is the formaldehyde content of the solution for each hourly sample in milligrams (mg) divided by the area of the exposed, unsealed surface in square metres (m²);
- i is the first, second or third or fourth hour;
- A_S is the absorbance of the solution from the wash bottles;
- A_B is the absorbance of distilled water;
- f is the slope of the calibration curve for standard formaldehyde solution, in milligrams per millilitre (mg/ml);
- F is the combined area of the emitting (unsealed) surface, in square metres (m²) (see [7.1](#));
- V is the volume of the volumetric flask, in millilitres (ml).

9.2 Calculation of results

9.2.1 Calculation of results of test pieces

If the formaldehyde content of the liquid absorbent accumulated during the 1st hour is lower than that of the 2nd hour, the formaldehyde yield shall be calculated from the sum of the contents collected during the 2nd to the 3rd or 4th hour and is related to the surface area, F , of the test pieces. If the formaldehyde accumulated in the 1st hour is equal to or greater than that of the 2nd hour, the sum of all three or four hourly samples shall be used in the calculation.

Consequently, the arithmetic average formaldehyde gas analysis value, G_m , in milligrams per square metre and hour (mg/m²h) of a test piece is calculated considering the test period used to determine the formaldehyde release (see [8.3.1](#)) according to either [Formula \(3\)](#) or [\(4\)](#) (test period of 3 h) or [Formula \(5\)](#) or [\(6\)](#) (test period of 4 h):

Determination of formaldehyde release using a 3 h test period:

$$G_m = \frac{G_2 + G_3}{2} \quad (3)$$

or

$$G_m = \frac{G_1 + G_2 + G_3}{3} \quad (4)$$

Determination of formaldehyde release using a 4 h test period:

$$G_m = \frac{G_2 + G_3 + G_4}{3} \quad (5)$$

or

$$G_m = \frac{G_1 + G_2 + G_3 + G_4}{4} \quad (6)$$

where G_m is the average gas analysis value of a test piece, in milligrams formaldehyde per square metre and hour ($\text{mg}/\text{m}^2\text{h}$).

As a rule, the formaldehyde content of the liquid absorbent accumulated during the 1st hour is lower than that of the 2nd hour as the temperature of the test piece does not reach 60 °C immediately.

9.2.2 Calculation of emission report value

Calculate the gas analysis value of the sample as the mean value of the, G_m , values of the two test pieces.

If three replicates are carried out (see 8.1), calculate the gas analysis value as the mean value of all three, G_m , values of the test pieces unless

- the average, G_m , value is $>1,0 \text{ mg}/\text{m}^2\text{h}$ and one replicate deviates more than 20 % of the closest value. Then, calculate the gas analysis value as the mean value of the remaining two, G_m , values, or
- the average G_m value is $\leq 1,0 \text{ mg}/\text{m}^2\text{h}$ and one replicate deviates more than $0,2 \text{ mg}/\text{m}^2\text{h}$ of the closest value. Then, calculate the gas analysis value as the mean value of the remaining two, G_m , values.

Results shall be expressed to one decimal place.

9.3 Moisture content

See ISO 16979.

10 Test report


The test report shall be in accordance with ISO 16999 and shall contain if known the following additional information:

- a) a reference to this document, i.e. ISO 12460-3:2020;
- b) origin of the board;
- c) place, location¹⁾, and state²⁾ of the board at the time of sampling;
- d) type of board;

1) For example, factory, etc. in the case of installed boards, ceiling, floor, wall, etc.

2) For example, moisture content, surface coating, finishing.

- e) thickness of board (mm);
- f) density of board (kg/m^3);
- g) date of manufacture of the board;
- h) date of sampling;
- i) information referring to the board regarding finishing, sanding, etc.;
- j) date of formaldehyde determination;
- k) age and treatment (preconditioning) of the sample before analysis (e.g. plywood or foil);
- l) the option used for formaldehyde determination (see 8.3.2 to 8.3.5), the formaldehyde average gas analysis value of the sample (see 9.2.2) together with each individual, G_m , value (see 9.2.1), in milligrams formaldehyde per square metre per hour ($\text{mg/m}^2\text{h}$);
- m) deviations from the procedures described in document (e.g. dimension of test piece);
- n) if requested, moisture content of sample at the time of testing (see ISO 16979);
- o) limit of quantification, in milligrams formaldehyde per square metre per hour ($\text{mg/m}^2\text{h}$);
- p) estimated uncertainty of measurement, in percent (%) or in in milligrams formaldehyde per square metre per hour ($\text{mg/m}^2\text{h}$).

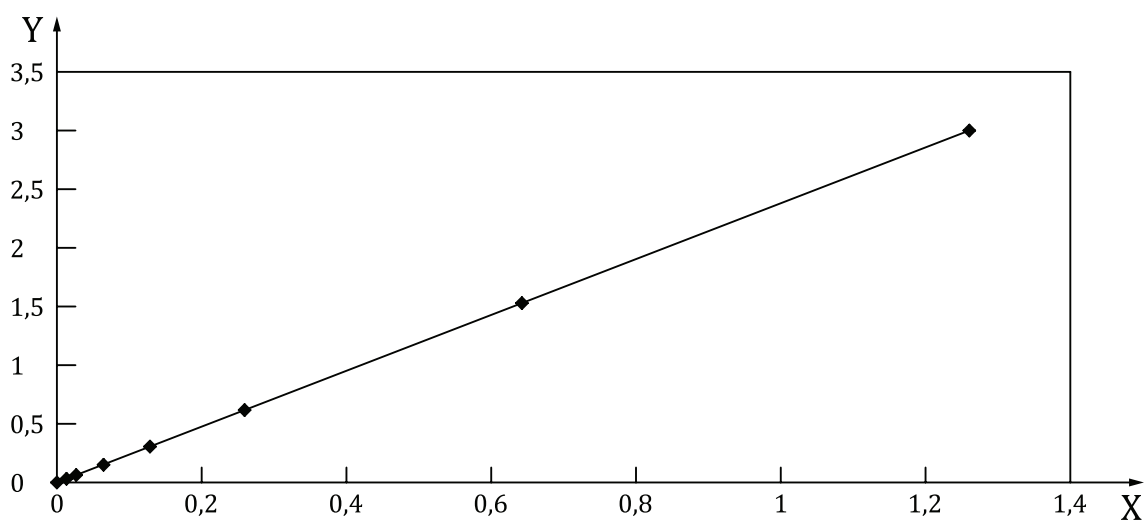

Key

X absorbance $A_S - A_B$

Y concentration of the diluted calibration solution, c (10^{-3} mg/ml)

Figure 2 — Example of a calibration curve for formaldehyde determined by acetylacetone method (path length 50 mm)

Bibliography

- [1] ISO 2227, *Formaldehyde solutions for industrial use — Determination of formaldehyde content*
- [2] ISO 12460-1, *Wood-based panels — Determination of formaldehyde release — Part 1: Formaldehyde emission by the 1-cubic-metre chamber method*
- [3] ISO 12460-4, *Wood-based panels — Determination of formaldehyde release — Part 4: Desiccator method*
- [4] ISO 12460-5, *Wood-based panels — Determination of formaldehyde release — Part 5: Extraction method (called the perforator method)*
- [5] ISO 14184-1, *Textiles — Determination of formaldehyde — Part 1: Free and hydrolysed formaldehyde (water extraction method)*
- [6] EN 717-1, *Wood-based panels — Determination of formaldehyde release — Part 1: Formaldehyde emission by the chamber method*

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Copyright in BSI publications

All the content in BSI publications, including British Standards, is the property of and copyrighted by BSI or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use.

Save for the provisions below, you may not transfer, share or disseminate any portion of the standard to any other person. You may not adapt, distribute, commercially exploit or publicly display the standard or any portion thereof in any manner whatsoever without BSI's prior written consent.

Storing and using standards

Standards purchased in soft copy format:

- A British Standard purchased in soft copy format is licensed to a sole named user for personal or internal company use only.
- The standard may be stored on more than one device provided that it is accessible by the sole named user only and that only one copy is accessed at any one time.
- A single paper copy may be printed for personal or internal company use only.

Standards purchased in hard copy format:

- A British Standard purchased in hard copy format is for personal or internal company use only.
- It may not be further reproduced – in any format – to create an additional copy. This includes scanning of the document.

If you need more than one copy of the document, or if you wish to share the document on an internal network, you can save money by choosing a subscription product (see 'Subscriptions').

Reproducing extracts

For permission to reproduce content from BSI publications contact the BSI Copyright and Licensing team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email cservices@bsigroup.com.

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Useful Contacts

Customer Services

Tel: +44 345 086 9001

Email: cservices@bsigroup.com

Subscriptions

Tel: +44 345 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK